

Determining 2018

By Hariyadi Soetedjo

WORD COUNT

1881

TIME SUBMITTED

15-OCT-2019 07:23AM

PAPER ID

51180592

Determining the degree of heat treatment of wood by light polarization technique

**Hariyadi Soetedjo, Ilpo Niskanen,
Lauri Rautkari, Michael Altgen, Eero
Hiltunen, Göran Thungström, Daniel
Zakrisson & Jukka Rätty**

11

**European Journal of Wood and Wood
Products**

Holz als Roh- und Werkstoff


ISSN 0018-3768

Volume 76

Number 4

Eur. J. Wood Prod. (2018) 76:1359-1362

DOI 10.1007/s00107-018-1311-2

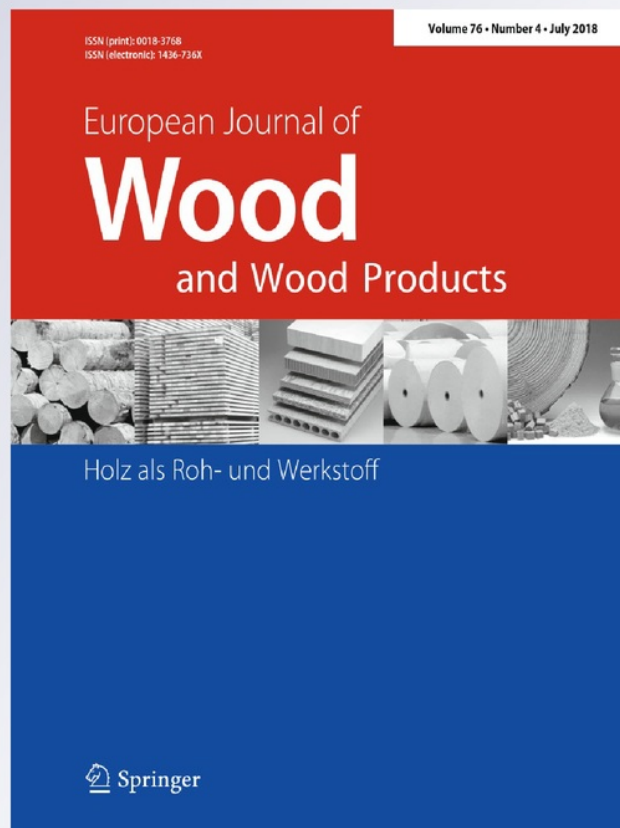

 Springer

Your article is protected by copyright and all rights are held exclusively by Springer-Verlag GmbH Germany, part of Springer Nature. This e-offprint is for personal use only and shall not be self-archived in electronic repositories. If you wish to self-archive your article, please use the accepted manuscript version for posting on your own website. You may further deposit the accepted manuscript version in any repository, provided it is only made publicly available 12 months after official publication or later and provided acknowledgement is given to the original source of publication and a link is inserted to the published article on Springer's website. The link must be accompanied by the following text: "The final publication is available at link.springer.com".



Determining the degree of heat treatment of wood by light polarization technique

Hariyadi Soetedjo¹ · Ilpo Niskanen^{2,3} · Lauri Rautkari⁴ · Michael Altgen⁴ · Eero Hiltunen⁴ · Göran Thungström³ · Daniel Zakrisson³ · Jukka Rätty⁵

10
Received: 23 October 2017 / Published online: 24 April 2018
© Springer-Verlag GmbH Germany, part of Springer Nature 2018

Abstract

Thermal modification of wood enables the use of non-durable wood species in exterior applications, but quality control methods are required to monitor the product variability. This study tests the potential of a light polarization technique where visible light (400–500 nm) is directed through a linear polarizer to the surface of thermally modified wood to measure the reflectance. Besides an effect of the grain direction, the reflectance decreased with increasing temperature during the thermal modification process. The technique could be used for quality control, but further studies are required to understand its modes of action.

1 Introduction

Thermal modification of wood is increasingly recognized as an environmental friendly technique to enable the exterior application of non-durable wood species. Thermal modification is based on exposing the wood to elevated temperatures (ca. 180–220 °C) to induce chemical changes that improve the resistance to fungal decay and the dimensional stability at the cost of reduced strength and ductility (Hill 2006). However, the increasing production volume and rising number of manufacturers in recent years necessitates the implementation of quality control systems. This requires methods that can rapidly quantify the changes of the wood caused by

temperature exposure to monitor the variability of thermally modified wood. A large number of quality control methods has already been evaluated. However, many of these methods require matched, untreated raw material, are destructive, or otherwise unsuitable for routine field quality control (Willem et al. 2015). Therefore, the development of new quality control methods is still desirable.

One potential method is the determination of the change in the optical constant of thermally modified wood. In a previous article by Niskanen et al. (2012), the effective refractive index of unmodified and thermally modified wood was measured using an immersion liquid method. The method is based on matching the refractive index of small wood particles with that of an immersion liquid. A clear effect of the temperature applied during the thermal modification on the effective refractive index was found, which indicated a loss in birefringence. However, the immersion liquid method requires sample preparation, is slow to conduct and typically requires expensive and toxic immersion liquids. The purpose of this paper is to investigate if the change in optical properties of wood by thermal modification can be determined by measuring the changes in polarized light reflectance from the surface of solid wood using a polarimeter and spectrophotometer techniques. Set-up based on these techniques can be simple and inexpensive.

20
✉ Hariyadi Soetedjo
hariyadi@uad.ac.id

1 Center for Integrated Research and Innovation (CIRNOV), The University of Ahmad Dahlan, Jalan Cendana No 9A, Yogyakarta, Yogyakarta 55166, Indonesia

2 Faculty of Technology, Structures and Construction Technology, University of Oulu, P.O. Box 7300, 90014 Oulu, Finland

3 Department of Electronics Design, Mid Sweden University, Umeå, Umeå 85170 Sundsvall, Sweden


4 Department of Bioproducts and Biosystems, School of Chemical Engineering, Aalto University, P. O. Box 16300, 00076 Aalto, Finland

5 Institute of Measurement Technology (MITY), University of Oulu, Technology Park 127, 87400 Kajaani, Finland

2 Materials and methods

Thermal modification of the samples was performed according to the Thermowood® process. Sawn timber (Scots pine, *Pinus sylvestris* L.) was modified in a kiln with a capacity of 0.5 m³. The timber with dimensions of 63 (H) × 75 (W) × 2000 (L) mm³ was treated at 160, 180, 200, 220, and 230 °C with heat treatment time of 3 h at the maximum temperature. The boards were sawn from trees that had grown in Central Finland, approximately between 64–65°N and 27–28°E and contained both heartwood and sapwood. Samples with dimensions of 4 (H) × 20 (W) × 180 (L) mm³ were cut from the heat-treated boards. The samples were measured in a laboratory that was conditioned at 23.5 °C and 50% relative humidity. Directly after measurements, density and moisture content of the samples were recorded. Dry mass for moisture content calculation was determined after 16 h of oven-drying at 105 °C. The experimental configuration is shown in Fig. 1. In the setup, a linear polarizer is adjusted to 45° with respect to xy-co-ordinate. The light source is a LED (Flash model 205 365) and optical power of 1.35W within the 400–500 nm wavelength range. The light passed through a linear polarizer towards the surface of a wood sample. The reflected light is detected by a spectrometer (ASEQ Instruments, model LR1). In the measurements, the incident angle was 60°, which is close to the Brewster angle of the air/wood-interface (at the Brewster angle, the reflected beam is polarized). The

Fig. 1 Schematic illustration of the optical set-up

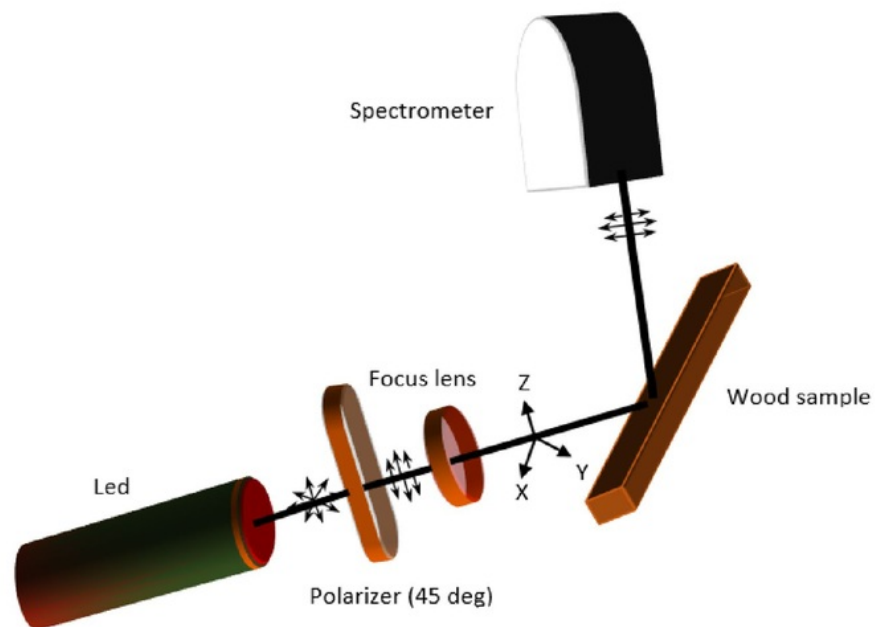

12

reflectance was calculated by dividing the reflected light intensity by the incident light intensity. The samples were measured in the vertical (y-axis) and horizontal (x-axis) grain directions with respect to the polarization direction of the incoming light beam. This method may introduce significant difference of reflected intensity between those different polarization directions at the same point of the sample being measured.

3 Results and discussion

Reflectance as a function of the wavelength in two grain directions is displayed in Fig. 2. The maximum reflectance is located at 447 nm for all thermal modification processes in both grain directions. The maximum reflectance was lower for the measurement in vertical direction (Fig. 2a) compared to the measurement in horizontal direction (Fig. 2b). This might be the result of the orientation of cellulose microfibrils in the wood cell wall, with almost longitudinal orientation in the largest (S2) layer of the cell wall. However, irrespective of the grain direction, the reflectance decreased by thermal modification, as evident from the data shown in Table 1. This decrease in reflectance is in line with a loss in birefringence of Scots pine wood by thermal modification observed as an increase in the effective refractive index by Niskanen et al. (2012). They explained the loss in birefringence by the penetration of the immersion liquid into cell wall pores created during thermal modification and by the deformation of crystalline cellulose. However, crystalline

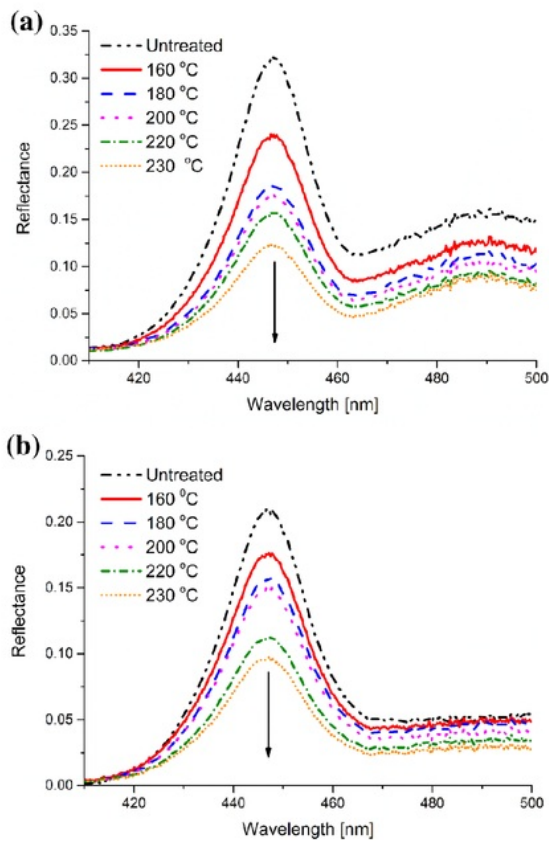


Fig. 2 Reflectance for different heat treatment degrees as a function of wavelength: **a** horizontal and **b** vertical grain direction

cellulose is highly resistant to heat and only little cellulose degradation occurs below 230 °C in hydrothermal treatments (Garrote 1999). The preferential degradation of hemicelluloses even results in an increase in percentage of crystalline

cellulose within the modified wood (Andersson et al. 2005). Therefore, other explanations should be considered for the decrease in reflectance.

Neither density nor the moisture content of the samples determined directly after the reflectance measurements (see Table 1) fully correlate with the monotonic decrease in reflectance. However, thermal modification is known to increase the number of chromophores in wood that absorb visible light (390–700 nm), with this increase being closely correlated to the temperature and duration applied. Chemical changes in both, the hemicelluloses and the lignin fraction, are involved in creating chromophores, but changes in the acid insoluble lignin fraction are believed to have the largest share in their formation (González-Peña and Hale 2009). The chromophores formed during thermal modification might also absorb the polarized light in the 400–500 nm wavelength range to decrease the reflectance, as measured in this study. Although further studies are required to understand the exact cause for the loss in reflectance, its simplicity, low costs, little measurement time and high sensitivity to the process conditions applied make the polarized light reflectance measurement a promising candidate for routine field quality control of thermally modified wood.

Table 1 Measurement results for thermally modified Scots pine

Degree of heat treatment (°C)	Density (g/cm ³)	Moisture content (%)	Reflectance of spectral polarimeter		Effective refractive index ^a
			Vertical	Horizontal	
Untreated	0.512	10.2	0.209 ± 0.01	0.321 ± 0.02	1.553
160 °C	0.471	7.5	0.176 ± 0.01	0.239 ± 0.01	1.578
180 °C	0.448	8.8	0.159 ± 0.01	0.185 ± 0.01	1.587
200 °C	0.423	6.5	0.150 ± 0.01	0.174 ± 0.01	1.587
220 °C	0.426	5.8	0.113 ± 0.01	0.156 ± 0.01	1.596
230 °C	0.436	4.9	0.097 ± 0.01	0.121 ± 0.01	1.596

^aDerived from Niskanen et al. (2012)

Acknowledgements The authors would like to express their thanks to Mr. Miftakudin for the technical assistance in CIRNOV's laboratory, The University of Ahmad Dahlan, Indonesia.

References

- 1 Andersson S, Serimaa R, Vaananen T, Paakkari T, Jämsä S, Viittemäki P (2005) X-ray scattering studies of thermally modified Scots pine (*Pinus sylvestris* L.). *Holzforschung* 59(4):422–427
- 2 Hill CAS (2006) *Wood modification: chemical, thermal and other processes*. John Wiley, Chichester
- 3 Garrote G (1999) Hydrothermal processing of lignocellulosic materials. *Holz Roh- Werkst* 57(3):191–202
- 4 Niskanen I, Heikkinen J, Mikkonen J, Harju A, Heräjärvi H, Venäläinen M, Peiponen KE (2012) Detection of the effective refractive index of thermally modified Scots pine by immersion liquid method. *J Wood Sci* 65:46–50
- 5 Willems W, Lykidis C, Altgen M, Clauder L (2015) Quality control methods for thermally modified wood. *Holzforschung* 69(7):875–884
- 6 **Publisher's Note** Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Determining 2018

ORIGINALITY REPORT

16%

SIMILARITY INDEX

PRIMARY SOURCES

- 1** www.doria.fi Internet 29 words — 2%
- 2** M. Wentzel, A. Rolleri, H. Pesenti, H. Militz. "Chemical analysis and cellulose crystallinity of thermally modified Eucalyptus nitens wood from open and closed reactor systems using FTIR and X-ray crystallography", European Journal of Wood and Wood Products, 2019 Crossref 29 words — 2%
- 3** jwoodscience.springeropen.com Internet 27 words — 1%
- 4** revistas.ubiobio.cl Internet 20 words — 1%
- 5** onlinelibrary.wiley.com Internet 19 words — 1%
- 6** pub.epsilon.slu.se Internet 18 words — 1%
- 7** Luna Goswami. "Stress generation in the tension wood of poplar is based on the lateral swelling power of the G-layer", The Plant Journal, 11/2008 Crossref 17 words — 1%
- 8** Ilpo Niskanen, Janne Lauri, Jukka Rätty, Rauno Heikkilä et al. "Monitoring drying process of varnish by immersion solid matching method", Progress in Organic Coatings, 2019 Crossref 17 words — 1%

9	www.sensorsportal.com Internet	17 words — 1%
10	xulab.org Internet	16 words — 1%
11	repo.pw.edu.pl Internet	15 words — 1%
12	shareok.org Internet	13 words — 1%
13	www.yumpu.com Internet	12 words — 1%
14	Michael Altgen, Tamás Hofmann, Holger Militz. "Wood moisture content during the thermal modification process affects the improvement in hygroscopicity of Scots pine sapwood", <i>Wood Science and Technology</i> , 2016 Crossref	12 words — 1%
15	www.mdpi.com Internet	11 words — 1%
16	Miha Humar, Davor Kržišnik, Boštjan Lesar, Nejc Thaler, Aleš Ugovšek, Klemen Zupančič, Mojca Žlahtič. "Thermal modification of wax-impregnated wood to enhance its physical, mechanical, and biological properties", <i>Holzforschung</i> , 2017 Crossref	9 words — < 1%
17	René Herrera-Díaz, Víctor Sepúlveda-Villarroel, José Torres-Mella, Linette Salvo-Sepúlveda et al. "Influence of the wood quality and treatment temperature on the physical and mechanical properties of thermally modified radiata pine", <i>European Journal of Wood and Wood Products</i> , 2019 Crossref	9 words — < 1%
18	www.mila.oulu.fi Internet	8 words — < 1%

19 Katja Vahtikari, Lauri Rautkari, Tuula Nojonen, Kristiina Lillqvist, Mark Hughes. "The influence of extractives on the sorption characteristics of Scots pine (*Pinus sylvestris* L.)", *Journal of Materials Science*, 2017
6 words — < 1%
Crossref

20 Hariyadi Soetedjo, Jukka Rätty. "Use of a modified Drude's equation to investigate the optical rotation property of sugars", *Optik - International Journal for Light and Electron Optics*, 2014
6 words — < 1%
Crossref

EXCLUDE QUOTES OFF
EXCLUDE BIBLIOGRAPHY OFF

EXCLUDE MATCHES OFF