

The Effect of Electrolyte Concentration on The Sensitivity of Low-Temperature Sensor Performance of Cu/Ni Film

By M. TOIFUR

The Effect of Electrolyte Concentration on The Sensitivity of Low-Temperature Sensor Performance of Cu/Ni Film

Danurdara Setiamukti¹, Moh. Toifur^{1*}, Azmi Khusnani¹

¹Physics Education Master, Ahmad Dahlan University, Jl. Pramuka No. 42 Pandeyan Umbulharjo Yogyakarta 55161 Indonesia

*Corresponding author: mtoifur@yahoo.com

Abstract

The purpose of this research is to make a low-temperature sensor with copper and nickel material or Cu/Ni film. The Cu/Ni film sensor is made by an electroplating method assisted by an external magnetic field of 200 G which is installed parallel to the deposition current. The Cu/Ni film is made by varying the concentration of the electrolyte solution. Next, the Cu/Ni film that was made was tested on LN₂ medium to measure its sensitivity value in response to changes in temperature. The results showed that the Cu/Ni film sensor could detect changes in LN₂ temperature. The results of data analysis showed that the curve relationship between voltage and temperature in the sample with the 2nd concentration state (C₂) had the highest relationship to influence each other between the voltage and temperature variables, and the sample had the highest sensitivity value compared to the others.

Keywords

Electrolyte Concentration, Sensitivity, Low-Temperature Sensor, Cu/Ni Film, Liquid Nitrogen, Magnetic Field.

Received: 20 March 2020, Accepted: 04 April 2020

<https://doi.org/10.26554/sti.2020.5.1.28-33>

1. INTRODUCTION

The National Research Master Plan has 10 strategic areas including food preservation namely in the 2015-2019 Food Industry No. 3 namely Preservation Technology (freezing, drying, preserving with sugar/salt) (RIRN 2017-2045) in order to increase Indonesia's fresh food export commodities so it is needed the development of cryogenic-based food preservation methods (Khadatkar et al., 2004; Goswami, 2010). Increased export-import activities on fresh food commodities in the international market led to the idea of developing new technology in the form of cryogenic freezers using liquid nitrogen (LN₂) called Cryofreezing.

The development of the curing method using liquid nitrogen media requires a tool that is able to detect changes in low temperature in LN₂ storage flasks. One type of low-temperature sensor that can be used is an RTD-based temperature sensor (Fraden, 2010; Chowdhury and Bulbul, 2010; Blasdel et al., 2015). The economical RTD sensor has been developed by Toifur et al. (2019, 2020) and Khusnani et al. (2019) with copper and nickel or Cu/Ni film. The results of the study stated that the weakness of this sensor is the response time to slow temperatures for temperatures below -150 °C while for temperatures above -150 °C the temperature response is fast. This is thought to be caused by the non-uniform surface morphology of the Ni deposit because there is no conditioning of Ni ions when diffusing onto the Cu

surface. The result of this is that the level of regularity of the Ni crystal structure is inconsistent following changes in deposition parameter settings.

The addition of magnetic fields aims to improve the morphological uniformity of Ni deposits (Yu et al., 2013; Zieliński et al., 2015). The role of parallel magnetic fields in the electrodeposition process is to form a regular pattern of Ni particle distribution on the substrate (Yamada and Asai, 2005). Thus the parallel magnetic field can also affect current efficiency, particle content of the coating, surface morphology, and the properties of the Ni coating (Zhou et al., 2013; Fattahi and Bahrololoom, 2015), increasing the mass transfer of metal ions significantly. The use of parallel fields is to magnetize electrolyte solutions. Decreased viscosity of electrolyte solutions and growth of hydrogen gas (Wu et al., 2014; Kumar and Sahoo, 2012), and increase the thickness of the coating structure (Jabbar et al., 2017). From these two aspects (parallel magnetic fields and electrolyte solution concentrations) it will produce a dense and homogeneous morphological structure of the layer.

Based on this, this study aims to make the Cu/Ni film assisted by a magnetic field parallel to the electrolyte concentration solution varied. The layer that has been obtained is then tested for its performance as a low-temperature sensor to see the sensitivity value of the sensor in response to changes in temperature.

2. EXPERIMENTAL SECTION

2.1 Materials

The Cu/Ni Film is made using the electroplating method. The materials used are copper (Cu) and nickel (Ni) plates of size (10 x 1.3) cm which are placed as cathodes and anodes. The electrolyte solution used in the deposition process consists of a mixture of H₃BO₃, NiSO₄, NiCl₂, and H₂O, with the composition listed in Table 1. The deposition process is carried out using an external magnetic field of 200 G, which is mounted parallel to the deposition current.

Table 1. The concentration of electrolyte solution

Conc.	H ₃ BO ₃ (g)	NiSO ₄ (g)	NiCl ₂ (g)	H ₂ O (mL)
C1	30	225	40	1000
C2	33	255	45	1000
C3	36	285	50	1000

2.2 Methods

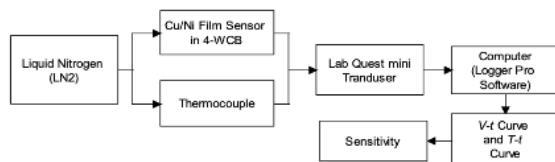


Figure 1. Flow-chart on the performance of Cu/Ni Film low-temperature sensor

The Cu/Ni film that has been formed, is tested for its performance as a low-temperature sensor to determine the sensitivity value of the sensor according to Figure 1. The sensor performance testing is carried out in liquid nitrogen with a temperature range between 0 °C to -170 °C by inserting the sensor slowly into the flask with a speed of 0.2 cm/s. Nitrogen flasks contain 10 liters of liquid nitrogen with a temperature difference between the top and the bottom. The output data is displayed in the form of an output voltage at various temperatures. This voltage varies depending on the temperature of the medium. Voltage variations occur due to changes in sensor resistance values. The temperature of the medium varies according to the depth of the flask. Voltage V and temperature T have a relationship:

$$V = aT^2 + bT + c \tag{1}$$

The relationship between the two variables V and T can be seen through the index of determination, R² (Toifur et al., 2014; Khusnani et al., 2019).

3. RESULTS AND DISCUSSION

The results of data retrieval are shown in Figure 2.

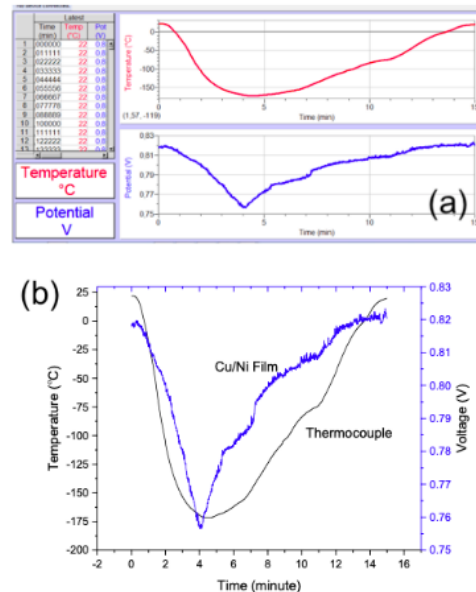


Figure 2. (a). The Data logger pro and (b). Time, voltage and temperature data on sensor performance measurement with voltage output data as data from Cu/Ni film sensors for samples with deposition at concentration 1 (C1)

Figure 2a displays a sample graph or Logger Pro data output for measuring low temperatures with thermocouple and Cu/Ni film sensors tested together in liquid nitrogen medium. Whereas in Figure 2b, the graph shows the relationship between voltage and temperature and time of the data in Figure 2a. Based on these results, it was concluded that the Cu/Ni film or the resulting Cu/Ni film sensor was able to respond to changes in temperature from liquid nitrogen.

Figure 2. a. The Data logger pro and b. Time, voltage and temperature data on sensor performance measurement with voltage output data as data from Cu/Ni film sensors for samples with deposition at concentration 1 (C1)

By observing Figure 2b, information can be obtained that the response of the two sensors between the thermocouple and the Cu/Ni film sensor is different. The Cu/Ni film sensor can respond to temperatures lower than the thermocouple which can detect changes in temperature up to > -170 °C and more quickly respond to changes in temperature rise between -170 °C to 20 °C. However, in response to changes in temperature from the range of 20 °C up to -170 °C, the response of Cu/Ni film sensors tends to be slower than thermocouple, this is because in that temperature range the thermocouple is more able to capture changes in temperature than the Cu/Ni film sensor.

The voltage, temperature and time data that have been obtained are then analyzed to find out the relationship between the voltage curve and the temperature of the sensor produced. The curve relationship is obtained by taking data from the range

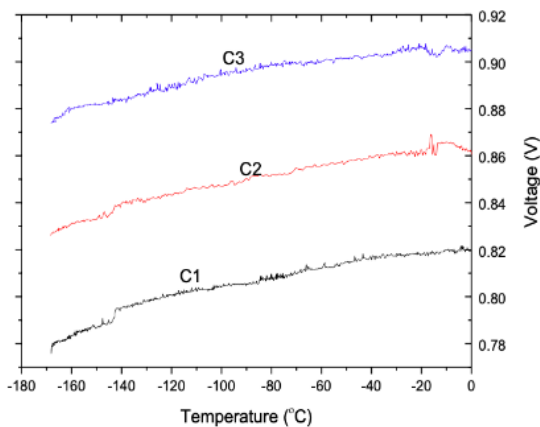


Figure 3. The output voltage and from the Cu/Ni film sample at changes in liquid nitrogen temperature from -170 °C - 0 °C.

-170 °C to 0 °C, as shown in Figure 3. The data is then processed using equation (1) so that the equation values obtained in table 2. Table 2 displays the coefficient values of a, b, c and the index of determination from the graph of the relationship between voltage and temperature.

Table 2. 2nd order polynomial fitting for each concentration

Conc.	2nd order polynomial fitting, $V=aT^2+bT+c$	Index of determination, R^2
C1	$V = -0,0012T^2 + 0,0296T + 819,24$	0,985
C2	$V = -0,0008T^2 + 0,0840T + 764,74$	0,988
C3	$V = -0,0009T^2 + 0,0182T + 829,05$	0,987

Based on the results of the 2nd order polynomial fitting, information can be obtained that is, the relationship between the voltage and temperature curves for the overall determination index value indicates a value exceeding 0.95. Based on this, both temperature stresses have a strong or mutually influential relationship (Rao et al., 2016b,a). The determination index value of the three samples is known that C2 has the highest value compared to the others with a value of 0.988. These results indicate that by giving effect to the amount of concentration with C2 levels, it gives a better relationship between stress and temperature than others.

The reliability of the sensor can be seen from the linearity and sensitivity (Toifur et al., 2020). Figure 4a shows a linearity graph between voltage and temperature. The slope of the linearity graph shows that the greater the slope obtained, the sensor in response to changes in temperature is more sensitive (Rao et al., 2016b,a). Based on this, it can be seen that the highest linearity is obtained by C2 and the lowest is obtained for C3. As for the sensitivity value shown in Figure 4b, where the highest sensitivity is owned by C2 with a value of 0.084 mV/°C and the lowest is obtained by the Cu/Ni film sensor for C3 with a value

of 0.018 mV/°C.

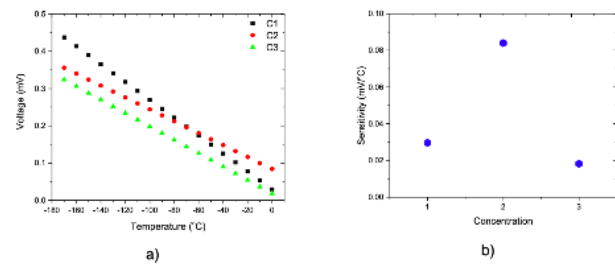


Figure 4. (a). linearity graph and (b) Sensitivity values for Cu/Ni film sensors on changes in liquid nitrogen temperature from -170 °C to 0 °C

The difference in yield at each concentration can be made possible due to the content of the material given in the manufacture of different electrolyte solutions. Basically, every material an electrolyte solution has different benefits, where NiS_4 acts as the main source of nickel ions, $NiCl_2$ has a role to help corrosion and increase the diffusion coefficient of nickel ions, while H_3BO_3 as a buffer (Birlik and Azem, 2018; Bouhidel and Rumeau, 2000; Budi et al., 2019). In this study, the amount of content of each ingredient made increases from C1 to C3 (according to table 1), but H_2O is made constant so that the most distinguishing of the three is the thickness of the mixture of these ingredients. The high amount of concentration or concentration of the material mixture shows that the amount of nickel ion availability is large (Schlesinger and Paunovic, 2011), by giving the effect of an external magnetic field parallel to the deposition current with a large magnetic field value that continues to influence the rate of Ni ions to the cathode which is different, this is because the dominant influence lies in the amount of ion content from each applied concentration.

4. CONCLUSIONS

Based on the research results obtained information that RTD-based sensors or Cu/Ni film sensors can detect changes in low temperature on LN2. The response of Cu / Ni film sensors is lower than that of thermocouple, whereas, for the rising temperature the opposite applies, the Cu/Ni film sensor is faster in responding to changes in rising temperature. The relationship between the voltage and temperature curve obtained that the sample with the state C2 has the highest relationship to influence each other between the voltage and temperature variables, and the sample has the highest sensitivity and the highest linearity compared to the others.

5. ACKNOWLEDGEMENT

This research is the preliminary research from the main research concerning with Cu/Ni temperature sensor. This research is funded by the Ministry of Research Technology and the Higher Education Republic of Indonesia through The 2020 Post Graduate Research Grant Year (PTM) Scheme.

REFERENCES

- Birlik, I. and N. F. A. Azem (2018). Influence of Bath Composition on the Structure and Properties of Nickel Coatings Produced by Electrodeposition Technique. *Deu Muhendislik Fakultesi Fen ve Muhendislik*, **20**(59); 689–697
- Blasdel, N. J., E. K. Wujcik, J. E. Carletta, K.-S. Lee, and C. N. Monty (2015). Fabric Nanocomposite Resistance Temperature Detector. *IEEE Sensors Journal*, **15**(1); 300–306
- Bouhidel, K.-E. and M. Rumeau (2000). Comparison of the electrolytic properties on NiSO₄ and NiCl₂: Influence of the salt nature in electro dialysis. *Desalination*, **132**(1-3); 195–197
- Budi, E., R. Theresia, I. Sugihartono, W. Indrasari, Y. Ermadiana, and D. Syafindra (2019). Electrodeposition of nickel-nitride composite coating: Effects of boric acid on structure and mechanical properties. In *AIP Conference Proceedings*. AIP Publishing
- Chowdhury, T. and H. Bulbul (2010). Design of a temperature sensitive voltage regulator for AC load using RTD. *International Journal of Engineering Science and Technology*, **2**(12); 7896–7903
- Fattahi, A. and M. Bahrololoom (2015). Investigating the effect of magnetic field on pulse electrodeposition of magnetic and non-magnetic nanostructured metals. *Surface and Coatings Technology*, **261**; 426–435
- Fraden, J. (2010). *Handbook of modern sensors*, volume 3. Springer
- Goswami, T. K. (2010). Role of Cryogenics in Food Processing and Preservation. *International Journal of Food Engineering*, **6**(1)
- Jabbar, A., G. Yasin, W. Q. Khan, M. Y. Anwar, R. M. Korai, M. N. Nizam, and G. Muhyodin (2017). Electrochemical deposition of nickel graphene composite coatings: effect of deposition temperature on its surface morphology and corrosion resistance. *RSC Advances*, **7**(49); 31100–31109
- Khadatkar, R., S. Kumar, and S. Pattanayak (2004). Cryofreezing and cryofreezer. *Cryogenics*, **44**(9); 661–678
- Khusnani, A., M. Toifur, G. Maruto, and Y. Pramudya (2019). The Effect of the Magnetic Field to the Microstructure and Sensitivity of Cu/Ni Film. *Universal Journal of Electrical and Electronic Engineering*, **6**(5B); 84–89
- Kumar, R. and N. Sahoo (2012). Design, Fabrication and Sensitivity Analysis of the Resistance Temperature Detector Thin Film Sensors. *International Journal of Mechanical and Industrial Engineering (IJMIE)*, **2**(4); 20–25
- Rao, S., G. Pangallo, and F. D. Corte (2016a). An Experimental Study on the Performance of Two Temperature Sensors Based on 4H-SiC Diodes. *Procedia Engineering*, **168**; 729–732
- Rao, S., G. Pangallo, and F. G. Della Corte (2016b). Integrated amorphous silicon pin temperature sensor for CMOS photonics. *Sensors*, **16**(1); 67
- Schlesinger, M. and M. Paunovic (2011). *Modern electroplating*, volume 55. John Wiley & Sons
- Toifur, M., B. Haryadi, and R. Riswanto (2014). Cow cement sensor based on coil-resistance temperature detector (c-rtd) coupled with four wire configuration bridge (4-WCB). In *2014 International Conference on Physics and its Applications (ICOPIA-14)*. Atlantis Press
- Toifur, M., A. Khusnani, and D. Okimustava (2019). Effect of Mass Fraction of Ni in Solution on the Microstructure and Sensitivity of Cu/Ni Film as Low-Temperature Sensor. *Universal Journal of Electrical and Electronic Engineering*, **6**(5B); 76–83
- Toifur, M., J. Saputra, A. Khusnani, and Okimustava (2020). The Effect Of Magnetic Field On The Performance Of Cu/Ni As Low-Temperature Sensor. *International Journal of Scientific and Technology Research*, **9**(1); 3526–3532
- Wu, W., N. Eliaz, and E. Gileadi (2014). The Effects of pH and Temperature on Electrodeposition of Re-Ir-Ni Coatings from Aqueous Solutions. *Journal of The Electrochemical Society*, **162**(1); D20–D26
- Yamada, T. and S. Asai (2005). Distribution control of dispersed particles in a film fabricated by composite plating method using a high magnetic field. *Journal of the Japan Institute of Metals*, **69**(2); 257–262
- Yu, Y. D., Z. L. Song, H. L. Ge, and G. Y. Wei (2013). Influence of magnetic fields on cobalt electrodeposition. *Surface Engineering*, **30**(2); 83–86
- Zhou, P., Y. Zhong, H. Wang, L. Fan, L. Dong, F. Li, Q. Long, and T. Zheng (2013). Behavior of Fe/nano-Si particles composite electrodeposition with a vertical electrode system in a static parallel magnetic field. *Electrochimica Acta*, **111**; 126–135
- Zieliński, M., E. Miękoś, D. Szczukocki, R. Dałkowski, A. Leniart, B. Krawczyk, and R. Juszcak (2015). Effects of constant magnetic field on electrodeposition of Co-W-Cu alloy. *International Journal Electrochemical Science*

The Effect of Electrolyte Concentration on The Sensitivity of Low-Temperature Sensor Performance of Cu/Ni Film

ORIGINALITY REPORT

5%

SIMILARITY INDEX

PRIMARY SOURCES

- 1 Muthi'ah Lutfia Khansa, Moh. Toifur, Azmi Khusnani, Yudhiakto Pramudya. "Deposition Time Variation on Thickness and Resistivity of Cu/Ni Thin Film Obtained by Magnetic Field-Assisted Electroplating Process", Journal of Physics: Conference Series, 2019
Crossref 20 words — 1%
- 2 aip.scitation.org
Internet 18 words — 1%
- 3 eprints.uny.ac.id
Internet 17 words — 1%
- 4 Lai, Meifang, Ching Tat Lai, Adrian Keating, John Dell, Yinong Liu, and Guy Metcalfe. "<title>Cross-flow microfiltration for lab-on-chip defatting of human breast milk</title>", Biomedical Applications of Micro- and Nanoengineering IV and Complex Systems, 2008.
Crossref 16 words — 1%
- 5 Moh. Toifur, Bagus Haryadi, Widya Rahmadani. "Prototype of low temperature sensor based on coils-resistance temperature detector enhanced with three-wire configurations bridge", Contemporary Engineering Sciences, 2015
Crossref 14 words — 1%
- 6 www.hrpub.org
Internet 9 words — < 1%
- 7 Victor Sunday Aigbodion, Enyi C.C., Akinlabi E.T., Suleiman I.Y., Ezema I.C., Mgbemene C.A.. 8 words — < 1%

"Morphology and properties of composite coating on mild steel:
effect of bath temperature and snail shell weight composition",
World Journal of Engineering, 2019

Crossref

EXCLUDE QUOTES

ON

EXCLUDE MATCHES

OFF

EXCLUDE
BIBLIOGRAPHY

ON