

HASIL CEK_Teja_TotokES IJAP

by Teja_totokes Ijap Artikel

Submission date: 06-Jan-2023 11:34AM (UTC+0700)

Submission ID: 1989078917

File name: Artikel Teja_TotokES IJAP 2014.pdf (855.58K)

Word count: 3182

Character count: 16078

The Effect of ZnO as Activator on Mechanical and Chemical Properties of Liquid Rubber Compound

Teja Dwi Sutanto^{1,3}, Bambang Setiaji², Karna Wijaya², Totok Eka Suharto³

¹Postgraduate student of Chemistry Department, Faculty of Mathematics and Natural Sciences, Gadjah Mada University, Yogyakarta, Indonesia.

²Department of Chemistry, Faculty of Mathematics and Natural Sciences, Gadjah Mada University, Yogyakarta, Indonesia.

³Department of Chemistry, Faculty of Mathematics and Natural Sciences, Bengkulu University, Bengkulu, Indonesia.

Telp : +6281367722099, Fax :-, email : tejasutanto44@yahoo.com

ABSTRACT

The effect of ZnO as activator on mechanical and chemical properties of liquid rubber compound has been examined. Liquid rubber made by mixing some chemicals such as stearic acid and Zinc Oxide as activator, BHT and liquid smoke as antioxidant, CaCO₃ as filler, MBTS and TMTD as accelerator, KOH as stabilizer and Sulphur as vulcanizing agent with concentrated latex at room temperature, then matured for 72 hours. In this research the use of ZnO as activator was varied as 7, 8, 9, 10 and 11 phr. Before being examined, rubber film made from liquid rubber compound by dyeing process then vulcanization done at 100 °C with water vapor. The rubber film which produced from liquid rubber compound then was characterized their mechanical and chemical properties such as resistance to heating, resistance to acid, alkaline resistance, solvent resistance and tear resistance. The result showed that ZnO content changed the mechanical and chemical properties of liquid rubber compound and obtained the best conditions on the use of 9 phr ZnO.

KEYWORDS: activator, liquid rubber compound, concentrated latex, additives, rubber film

INTRODUCTION

Liquid rubber compound is a mixture of natural rubber latex with various chemical additives to obtain the final result of vulcanizates with a particular process [1,2]. In the manufacture of rubber goods, liquid rubber is the result before the end of the process to obtain the finished rubber goods. In the process of making liquid rubber or compounding, chemical reaction will occur between polyisoprene of latex rubber with

a variety of chemicals that are used to form the three-dimensional cross linking between the molecules of the rubber material polyisoprene with vulcanizator such as sulphur that will improve nature of the original rubber to be more usable for manufacture rubber goods [3-6]. Liquid rubber compound chemicals generally consists of vulcanizator, accelerator, antioxidant ingredients, activator, stabilizer and filler as well as other supplemental materials [1, 2]. Latex rubber finished products generally have certain traits preferred, therefore, liquid rubber composition to be made adapted to the type of product to be produced or the nature of the preferred.

The raw material of liquid rubber compound is concentrated latex with most additive components solid so that the process of mixing or compounding would be more perfect if it is done by mixing various ingredients such additives in the liquid state is by first dispersing the various ingredients into liquid ingredients with the addition of certain dispersants so expect the resulting liquid rubber specification will be eligible to make a variety of rubber goods [7]

The problems that exist in the world rubber industry is the unavailability of liquid rubber or compound in large quantities ready to be used to make a variety of rubber goods as new liquid rubber is usually made prior to manufacture certain goods carried, in addition to compound usually made in the form of a dense mix of rubber material that has been frozen, then solid compound is dissolved if it will be made into a particular item [2].

The purpose of this research is to study the effect of variation in the use of ZnO as activator in the manufacturing process of liquid rubber compound on their changes of the mechanical and chemical properties which includes the resistance to heating or oxidation, resistance to acid, resistance to alkaline, resistance to solvent and tear resistance. Determination the changes of mechanical and chemical properties done by measuring the tensile strength and elongation at break of rubber films before and after a particular treatment [8-10].

EXPERIMENTAL SECTION

The process of making liquid rubber or rubber compound is the process of mixing the concentrated latex materials with different dispersion additives that have been made in advance. such as stearic acid and Zinc Oxide as activator, 3,5-di-tertbutyl-4-hydroxy toluene (BHT) and liquid smoke as antioxidant, CaCO₃ as filler, dibenzothiazole disulfide (MBTS) and tetramethyl thiuram disulfide (TMTD) as accelerator, KOH as stabilizer and Sulphur as vulcanizing agent [11]). The addition of chemicals do one at a time, stirring until homogeneous materials recently added next. After all the additive is added, the liquid rubber is then allowed to stand for 72 hours at room temperature for curing. Variation in this study to be carried out is the use of ZnO as activator [12,13]. The variation of the concentration of ZnO to be done is 7, 8, 9, 10, and 11 phr. To determine the quality of liquid rubber compound that produced, the first time made rubber film by means of dyeing, drying and vulcanization by heating in water vapor in order to obtain a rubber film with a thickness of from 0.01 to 0.11 mm in accordance with ASTM D-412 standard [14-18]. Further testing of the mechanical and chemical properties of rubber films include the resistance of heating,

the resistance of acid, the resistance of alkaline, the resistance of solvent and tear resistance [19,20]. All of these activities are done in the laboratory of plastics and Rubber Research Facility, Center for Leather, Rubber and Plastics Yogyakarta and in the Laboratory of Chemistry Faculty of Mathematics and Natural Sciences, Bengkulu University, Bengkulu.

RESULTS AND DISCUSSION

The results of this study indicate that increased levels of ZnO are used turned out to significantly affect the physical and chemical properties of the resulting liquid rubber.

1. Rubber Film

Tests performed with a liquid rubber compound first made rubber film by immersion followed by vulcanization at 100 °C by using a water vapor [16]. As an example of the resulting rubber film is presented in figure 1 below.



Figure 1. Rubber film

2 Resistance to Heating/Aging

From the picture above shows that the tensile strength of rubber films before and after ageing tends to increase if the use of ZnO is greater, reaching the best conditions on the variation of 9 phr ZnO, then turn down to the growing use of ZnO. In this condition the amount of tensile strength after aging of the rubber films obtained is 19,03 N/mm², this suggests that the formation process of crosslinking is most prevalent in this variation. In the picture above also shows that on the variation of 9 phr ZnO obtained rubber films most resistant to heating. This situation is caused by the use of ZnO is greater then the polyisoprene of latex will be more active so that the formation of crosslinks between polyisoprene with sulphur will more easily occur, reaching the optimum conditions on 9 phr ZnO. On the use of more ZnO are will cause coagulation of latex so that the formation of crosslinking will also decrease.

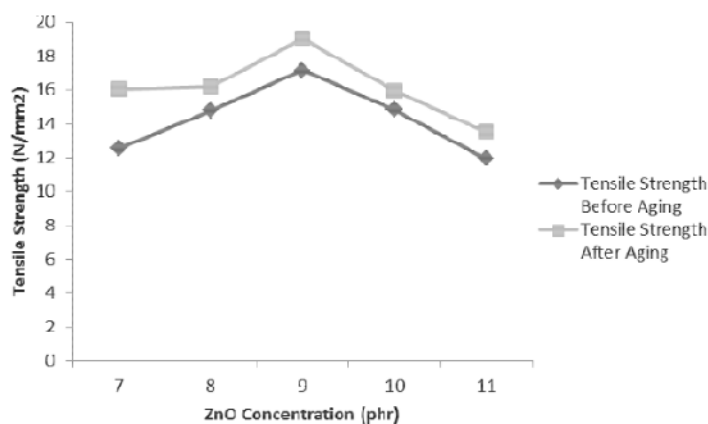


Figure 2. Tensile strength changes before and after ageing at various ZnO content

From the experimental results it is shown that a change in the content of ZnO used give little effect on the elongation at break of rubber films before and after ageing, as seen from the value of elongation at break before and after ageing is not much change in the variation used, but the best conditions of liquid rubber manufacture obtained on the variation of 9 phr ZnO. In this variation the value of elongation at break before and after ageing obtained as high as 812.07% and 766.14%. In this figure also shows that the elongation at break decreased at all levels of variation of ZnO used, it indicates that the rubber is more easily broken when heated.

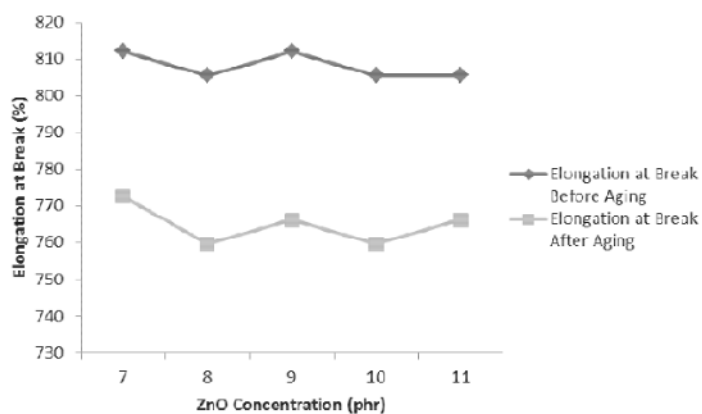


Figure 3. Elongation at break changes before and after ageing at various ZnO content

3. Resistance to Acid

In the picture above shows that the tensile strength of rubber films after immersion in acid tends to rise in the use of ZnO is increased, reaching a peak at the use of 9 phr ZnO and then decreased on the use of ZnO is more and more. This indicates that the rubber film more resistant to the acid on the use of ZnO is more and more. This situation is due to the use of ZnO is more and more the formation of crosslinks between polyisoprene of latex with sulphur will be more and more because polyisoprene more active, so the number of crosslinks formed are also increasingly causing rubber film more resistant to acid. On the use of greater ZnO just turned to coagulation of polyisoprene then resulting the decrease in the number of crosslinks formed and consequently the resistance to acid also decreased. In the best conditions tensile strength data obtained before and after immersion in acid are 17.17 N/mm² and 14.90 N/mm².

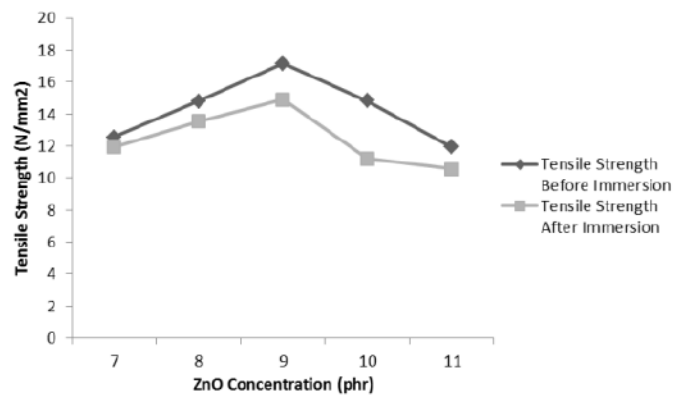


Figure 4. Tensile strength changes before and after immersion in acid at various ZnO content

In the picture above shows that immersion in acid affects the elongation at break of rubber film, it is seen from the change of elongation at break before and after immersion in acid. In this figure also shows that the elongation at break initially fell and then rose and reached a peak at 9 phr ZnO, and then decreases again at higher concentration of ZnO. This is because the amount of crosslinking between sulphur and polyisoprene reach maximum number in use of 9 phr ZnO. At levels below 9 phr the amount of crosslinking that occurs is not maximized yet, while at higher levels has decreased due to the coagulation of liquid rubber during the manufacturing process. At best condition elongation at break of rubber film after immersion in acid is 903.94%.

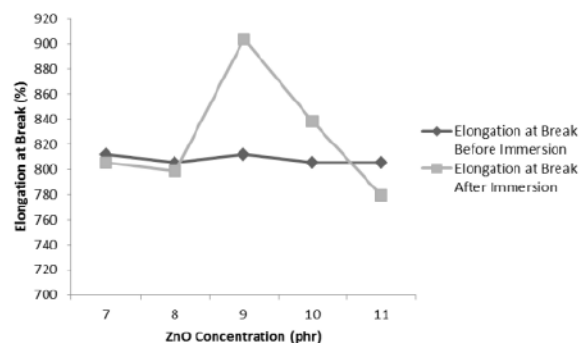


Figure 5. Elongation at break changes before and after immersion in acid at various ZnO content

4. Resistance to Alkaline

In the picture above shows that the rubber film made more resistant to bases on the use of ZnO is more and more, achieve the best conditions on the use of ZnO 9 phr, and then decreased at the use of ZnO is more and more. It is seen from the greater value of tensile strength after immersion in alkaline if the use of ZnO is more and more and then decreased after 9 phr ZnO. These condition indicate that the formation of crosslinks between the sulphur and polyisoprene more and more on the growing use of ZnO. Crosslinking formation reach peak at 9 phr ZnO and decrease on the use of ZnO is greater. On the use of ZnO is slightly then polyisoprene still less active so the number of crosslinks formed is still small, but in the use of ZnO larger than 9 phr, it causes coagulation of polyisoprene so the number of crosslinks formed also decrease. In the best condition showed that the tensile strength of rubber films after immersion in alkaline is 18.61 N/mm².

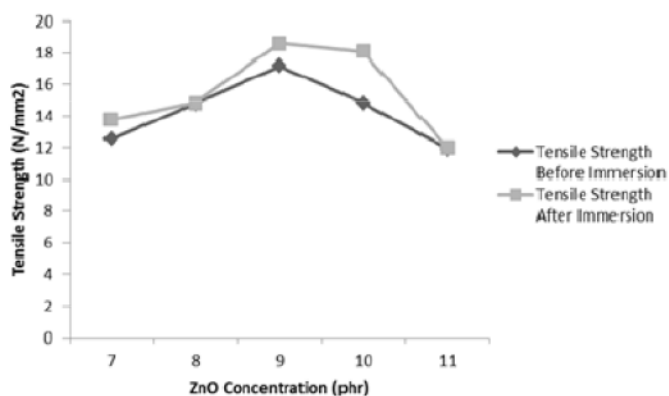


Figure 6. Tensile strength changes before and after immersion in alkaline at various ZnO content

In the picture above shows that the changes in the levels of ZnO affects the persistence of the rubber film to alkaline. It is seen from the increasingly value of elongation at break after immersion in alkaline on the use of ZnO is more and more, reaching a peak on the use of 9 phr ZnO and then decreases on the growing use of ZnO. This shows that the greater number of crosslinks between polyisoprene of latex with sulphur on the use of ZnO is more and more, reaching optimum condition at 9 phr ZnO, and then decreased at the use of ZnO more. In the best condition showed that elongation at break of rubber film after immersion in alkaline is 871.13%.

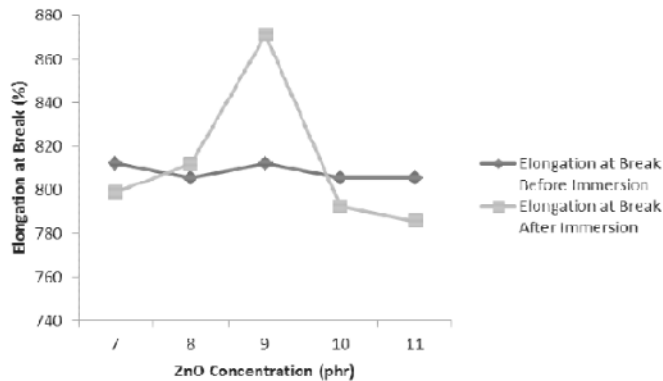


Figure 7. Elongation at break changes before and after immersion in alkaline at various ZnO content

5. Resistance to solvent

In the picture above shows that the number of fractions dissolved in acetone tends to slight on the growing use of ZnO, reaching a minimum at the concentration of 9 phr ZnO, then rise to higher levels of ZnO. This indicates that the rubber film more resistant to solvents on the use of ZnO are getting bigger, but will decrease again on the use of ZnO larger than 9 phr. This condition caused by the amount of crosslinking between polyisoprene of latex with sulphur that more and more if the use of ZnO are more and more, but in the use above 9 phr of ZnO, the amount of crosslinking that occurs has increased due to the occurrence of coagulation process during the manufacture of liquid rubber compound. In the best condition showed that the soluble fraction in the acetone is 0.0488.

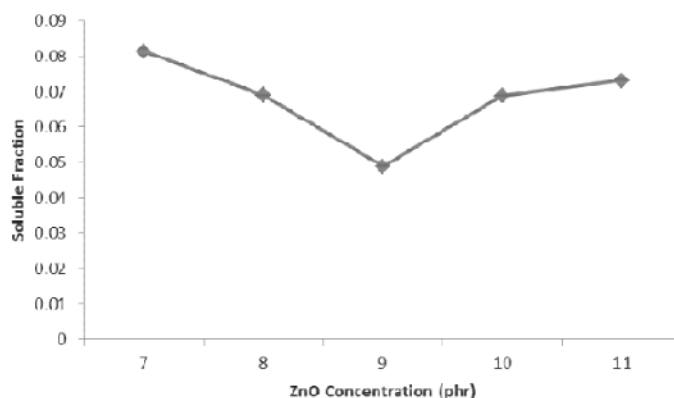


Figure 8. Effect of ZnO concentration on Rubber film solubility in acetone

6. Tear resistance

In the picture above shows that the tear resistance of rubber films the greater the use of ZnO is more and more, reaching a peak on the use of ZnO as many as 9 phr, and then decreased to the growing use of ZnO. This situation is due to the use of ZnO more and more then the polyisoprene of latex will be more active so that the formation of crosslinks between polyisoprene with sulphur will be more and achieve optimum condition at 9 phr ZnO. On the use of ZnO is higher then the formation of crosslinks will actually decrease due to the coagulation of polyisoprene in the manufacture process of liquid rubber compound. At the optimum conditions obtained data that the tear strength of rubber film is 7,10 N/mm².

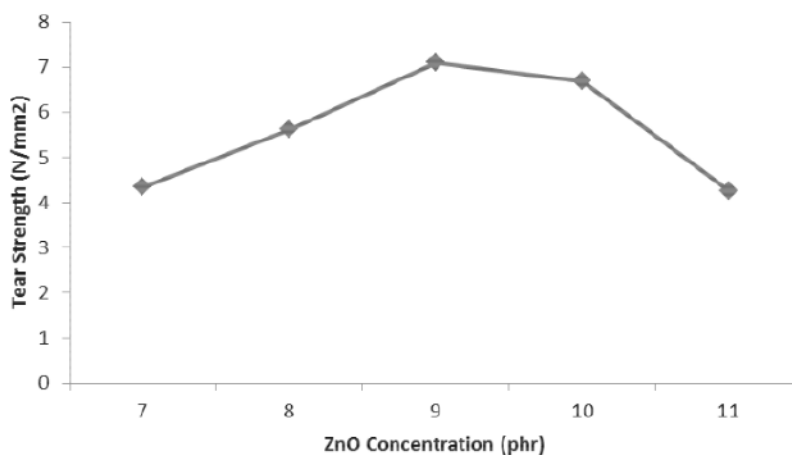


Figure 9. Effect of ZnO content on tear resistance

CONCLUSION

The use of ZnO as activator variation changed the mechanical and chemical properties of liquid rubber compound produced. The best condition was the use of 9 phr ZnO concentration. The mechanical and chemical properties of liquid rubber compound as rubber film produced in this condition are tensile strength before and after heating 17.17 N/mm² and 19.03 N/mm²; elongation at break before and after heating 812.07% and 766.14%; tensile strength after immersion in acid 14.90 N/mm²; elongation at break after immersion in acid 903.94%; tensile strength after immersion in alkaline 18.61 N/mm²; elongation at break after immersion in alkaline 871.13%; dissolved fraction in acetone 0.0488 and tear resistance 7,10 N/mm².

ACKNOWLEDGMENTS

The author would like to thank the Center for Leather, Rubber and Plastic, Yogyakarta; Department of Chemistry, Faculty of Mathematics and Natural Sciences, Gadjah Mada University, Yogyakarta; Department of Chemistry, Faculty of Mathematics and Natural Sciences, Bengkulu University, Bengkulu for the provision of laboratory facilities and Directorate General of Higher Education Ministry of Education and Culture of the Republic of Indonesia has been pleased to finance this research activity with the contract number 3220/UN30.10.06.01/HK/2013.

REFERENCE

- [1] Xu H., Han J., Fang L., Shen F. and Wu C., 2007, "Effect of Grafted Carbon Black on Properties of Vulcanized Natural Rubber," *Polymer Bulletin*, 58, 5-6, 951-962.
- [2] White J., De S.K. and Naskar, 2009, "Rubber Technology's Handbook Volume 2," *Smithers Rapra Technology Limited, Shawbury*, 281-287.
- [3] Khang T.H. and Ariff Z.M., 2012, "Vulcanization Kinetics Study of Natural Rubber Compounds Having Different Formulation Variables," *J. Therm. Anal. Calorim.*, 109, 3, 1545-1553.
- [4] El-Nemr K.F., 2011, "Effect of Different Curing System on the Mechanical and Physico-Chemical Properties of Acrylonitrile Butadiene Rubber Vulcanizates," *Material and Design*, 32, 6, 3361-3369.
- [5] Kumnuantip C. and Sombatsompop N., 2003, "Dynamic Mechanical Properties and Swelling Behaviour of NR/Reclaimed Rubber Blends," *Materials Letters*, 57, 21, 3167-3174.
- [6] Radhakrishnan C.K., Kumari P., Sujith A. and Unnikrishnan G., 2008, "Dynamic mechanical properties of styrene butadiene rubber and poly (ethylene-co-vinyl acetate) blends," *J. Polym. Res.*, 15, 2, 161-171.
- [7] Danwanichakul P., Lertsurasakda P. and Wiwattanasit R., 2012, "Correlation between dry rubber content in field latex and viscosity measured with efflux time method," *Songklanakarin J. Sci. Technol.*, 34, 5, 551-555.
- [8] Manoj K.C., Kumari P. and Unnikrishnan G., 2011, "Cure Characteristics,

- Swelling Behaviors, and Mechanical Properties of Carbon Black Filler Reinforced EPDM/NBR Blend System,” *Journal of Applied Polymer Science*, 120, 5, 2654-2662.
- [9] Robert C.C. and Francis L.F., 2013, “Drying and Cracking of Soft Latex Coatings,” *J. Coat. Technol. Res.*, 10, 4, 441-451
- [10] Brown R.P. and Butler T., 2000, “Natural Ageing of Rubber,” *Rapra Technology Ltd., Shawbury*, pp 2, 9, 19-34.
- [11] Rodrigues F.H.A., Feitosa J.P.A., Ricardo N.M.P.S., de Franca F.C.F. and Carioca J.O.B., 2006, “Antioxidant Activity of Cashew Nut Shell Liquid (CNSL) Derivatives on The Thermal Oxidation of Synthetic *cis*-1,4-polyisoprene,” *J. Braz. Chem. Soc.*, 17, 2, 1-10.
- [12] Przybyszewska M. and Zaborski M., 2009, “The Effect of zinc Oxide nanoparticle Morphology on Activity in Crosslinking of Carboxylated Nitrile Elastomer,” *Express Polymer Letters*, 3, 9, 542-552.
- [13] Jeon G.S., Han M.H. and Seo G., 1999, “Effect of ZnO Content at The Surface of Brass-Plated Steel Cord on The Adhesion Property to Rubber Compound,” *Korean J. Chem. Eng.*, 16 (2), 248-252.
- [14] Chiu H.T. and Tsai P.A., 2006, “Aging and Mechanical Properties of NR/BR Blends,” *Journal of Materials Engineering and Performance*, 15, 1, 88-94.
- [15] Sulekha P.B. and Joseph R., 2003, “Preparation and Characterisation of Novel Polymer Bound Phenolic Antioxidants and its Use in Natural Rubber,” *Journal of Elastomers and Plastics*, 35, 1, 85-97.
- [16] Huo D.X., Yuan X.Y., Liu D.Z., Zhang L. and Wang F., 2008, “Effect of The Phase Structure Evolution on The Properties of Films Formed from PBA/P(*St-co*-MMA) Composite Latex,” *Chinese Journal of Polymer Science*, 26, 1, 39-45.
- [17] Kan C.S., 1999, “Role of Particle Size on Latex Deformation During Film Formation,” *Journal of Coating Technology*, 71, 896, 89-97.
- [18] Lu Y., Zhang J., Chang P., Quan Y. and Chen Q., 2011, “Effect of Filler on the Compression Set, Compression Stress-Strain Behavior, and Mechanical Properties of Polysulfide Sealants,” *Journal of Applied Polymer Science*, 120, 4, 2001-2007.
- [19] Ochigbo S.S., Luyt A.S. and Focke W.W., 2009, “Latex Derived Blends of Poly (Vinyl Acetate) and Natural Rubber: Thermal and Mechanical Properties,” *J. Mater. Sci.*, 44, 12, 3248-3254.
- [20] Burford R.P. and Pittolo M., 1984, “The Mechanical Properties of Rubber Compounds Containing Soft Fillers,” *Journal of materials Science*, 19, 3059-3067

HASIL CEK_Teja_TotokES IJAP

ORIGINALITY REPORT

10%

SIMILARITY INDEX

8%

INTERNET SOURCES

10%

PUBLICATIONS

3%

STUDENT PAPERS

PRIMARY SOURCES

1	www.ripublication.com Internet Source	3%
2	Teja Dwi Sutanto, Charles Banon, Bambang Trihadi. "Effect of Liquid Rubber Compound on the Physicochemical Properties of Particle Board from Coconut Frond Powder", RAFFLESIA JOURNAL OF NATURAL AND APPLIED SCIENCES, 2022 Publication	2%
3	journal.ugm.ac.id Internet Source	1%
4	repository.itny.ac.id Internet Source	1%
5	www.kjrimumbai.net Internet Source	1%
6	Submitted to Syiah Kuala University Student Paper	<1%
7	pureportal.coventry.ac.uk Internet Source	<1%

8

T D Sutanto, C Banon, B Trihadi, N F Damayani. "Effect of Grain Size Coconut Frond Powder on The Strength of Particle Board", Journal of Physics: Conference Series, 2021

Publication

<1 %

9

Junko Adachi. "Cholesterol Hydroperoxides in Erythrocyte Membranes of Alcoholic Patients", Alcoholism Clinical and Experimental Research, 4/1999

Publication

<1 %

10

dyuthi.cusat.ac.in

Internet Source

<1 %

11

Ahmed Abdulameer Subeh, Mohammed H. Al-Maamori, Ahmed Fadhil Hamzah. " The Effect of the Nanoparticle SiO on the Mechanical and Physical Properties of Rubber Composites ", IOP Conference Series: Materials Science and Engineering, 2020

Publication

<1 %

12

journals.sagepub.com

Internet Source

<1 %

13

Yalan Li, Hao Sun, Yangyang Zhang, Min Xu, Sheldon Q. Shi. "The three-dimensional heterostructure synthesis of ZnO/cellulosic fibers and its application for rubber

<1 %

composites", Composites Science and Technology, 2019

Publication

Exclude quotes On

Exclude matches Off

Exclude bibliography On