

# HASIL CEK\_Artikel Chemica

*by Tind Artikel Chemica*

---

**Submission date:** 07-Jan-2023 03:21PM (UTC+0700)

**Submission ID:** 1989462432

**File name:** Artikel\_Chemica\_Totok-et\_al.pdf (624.82K)

**Word count:** 3439

**Character count:** 18144

## Green Synthesis of Sulfonated Activated Carbon from Palm Kernel Shell as Potential Catalyst for Hydrolysis of Palm Bunch Cellulose

Totok Eka Suharto<sup>a,1,\*</sup>, Cindy Wulandari<sup>b,2</sup>, Dwita Oktiarni<sup>b,3</sup>, Devi Ratnawati<sup>b,4</sup>, Ibdal Satar<sup>c,5</sup>

<sup>a</sup> Department of Chemical Engineering, Faculty of Industrial Technology, Universitas Ahmad Dahlan, Kampus 4 Ring Road Selatan, Tamanan, Bantul, Yogyakarta 55163, Indonesia

<sup>b</sup> Department of Chemistry, Faculty of Mathematics and Natural Sciences, Universitas Bengkulu, Jl. W.R. Supratman, Bengkulu 38371, Indonesia

<sup>c</sup> Department of Food Technology, Faculty of Industrial Technology, Universitas Ahmad Dahlan, Kampus 4 Ring Road Selatan, Tamanan, Bantul, Yogyakarta 55163, Indonesia

<sup>1</sup> [suharto@che.uad.ac.id](mailto:suharto@che.uad.ac.id), <sup>2</sup> [cindy.wulandari@yahoo.com](mailto:cindy.wulandari@yahoo.com), <sup>3</sup> [dwita@gmail.com](mailto:dwita@gmail.com), <sup>4</sup> [devi\\_r64@yahoo.com](mailto:devi_r64@yahoo.com), <sup>5</sup> [ibdal@tp.uad.ac.id](mailto:ibdal@tp.uad.ac.id)

\* corresponding author

### ARTICLE INFO

#### Article history

Received July 22, 2022

Revised December 14, 2022

Accepted December 16, 2022

#### Keywords

Cellulose

Hydrolysis

Palm shell waste

Sulfonated activated carbon

### ABSTRACT

Biofuels are currently attracting attention as an alternative solution to the issue of depleting petroleum reserves and environmental problems. Biofuels can be produced through the catalytic conversion of biomass. Sulfonated activated carbon (SAC) is an active catalyst for biomass conversion. Sulfonated activated carbon is one of the green catalysts that has been successfully synthesized from palm shell waste. The SAC catalysts were prepared from palm shell waste by converting to activated carbon followed by sulfonating step. The SAC catalysts were characterized by using XRD, SEM, FTIR, and gravimetric methods. The SAC catalysts are porous amorphous and have acidic properties, a prerequisite for good catalytic activity. Preliminary catalytic tests showed that the SAC catalysts can be used for the hydrolysis of cellulose from palm bunch waste which was shown by the existence of reducing sugar in the liquid product of hydrolysis.

13

This is an open-access article under the CC-BY-SA license.



## 1. Introduction

Biomass is the most abundant source of cellulose and could become an alternative to fossil resources for the sustainable production of chemicals and fuels. Many types of research have previously focused on the degradation of cellulose through some approaches such as the use of dilute acids, enzymes, and supercritical reactions. Principally, the conversion of cellulose into chemicals and/or fuels occurs through depolymerization reactions in acidic conditions with homogeneous catalysts, enzymes, and subcritical and supercritical water [1]. Based on the literature the major drawbacks of these methods include corrosion hazards, difficulties in separation from the mixture, control of enzymes, danger to the operator, and harsh reaction condition. Therefore, alternative catalysts are needed to overcome these issues. Several types of catalysts such as SAC, Al<sub>2</sub>O<sub>3</sub>, H-mordenite, HZSM-5, H-Beta, sulfated zirconia, and Amberlyst 15 have been used to hydrolyze cellulose into simple sugar [1],[6]. Among these catalysts, the SAC catalysts show the highest catalytic activity of about 70% conversion [6].

In general, the SAC could be synthesized from biomass resources such as coconut shells, coffee residue, coal, rice husk and straw, corncob, bamboo, chitosan, etc [2]-[5]. So far, there were only a few reports on using palm kernel shells to synthesize SAC catalysts. The utilization of palm plantation industrial waste in the form of empty fruit bunches and abundant palm kernel shells as raw material for the preparation of carbon-based catalysts. It was known that palm kernel shells can be used as a raw material for the synthesis of sulfonated activated carbon catalysts.

Biomass waste material has been used as a carbon precursor for the preparation of solid acid catalysts such as activated carbon [10] through the carbonization and activation processes. Due to the low catalytic performance of activated carbon for the hydrolysis of cellulose to simple sugar, so the sulfonation process is needed to improve the acidity and at the same time enhance the catalytic activity. Sulfonation is the process of attaching the sulfonate ( $-\text{SO}_3\text{H}$ ) group onto the activated carbon surfaces. The sulfonation process can be performed in mild conditions, is easy to handle, is inexpensive, and could be applied in various solid catalysts [10]-[12].

As mentioned above the SAC catalysts can be prepared from the palm kernel shell through the simple sulfonation process. This work tries to synthesize and characterize the SAC catalysts from palm kernel shells and to preliminary test of hydrolysis of cellulose from palm bunches. Some parameters such as crystallinity, and morphology acid properties to identify the SAC catalyst's properties. In addition, the Fehling test is also performed to identify the simple sugar as a product of cellulose hydrolysis.

## 2. Research Methodology

### 2.1. Materials

Raw materials used in the research are palm kernel shells and palm bunch cellulose obtained from a palm oil industry in Bengkulu. For the activation was used  $\text{ZnCl}_2$  (Merck, Germany) and for the sulfonation was used  $\text{H}_2\text{SO}_4$  98% (BASF, Germany).

### 2.2. Procedures

#### 1) Palm shell preparation

Palm kernel shells were collected from the waste of crude palm oil (CPO) factory in Bengkulu Indonesia. Palm kernel shells were separated from the waste mixture by soaking them in water and were then washed with water and dried in an oven at  $110^\circ\text{C}$  for 4 hours. The dried palm kernel shells were ground into small pieces, then carbonized in a furnace at a temperature of  $350^\circ\text{C}$  for about 2 hours, so that they become charcoal. After the material reaches room temperature, the obtained charcoal was milled into powder and sieved by 90 mesh. This dried charcoal powder was used as raw material to produce activated carbon (AC).

#### 2) Synthesis of sulfonated activated carbon (SAC)

The SAC catalyst was synthesized in two steps including the synthesis of activated carbon from palm kernel shells and the sulfonation steps, adopting the modified previous methods [2]-[5]. In the first step, the activation of charcoal has been performed by the physio-chemical method. Charcoal powder was mixed into 0.1 M zinc chloride solution with a ratio of 1:10 (w/v). The mixture was then soaked, heated at  $90^\circ\text{C}$ , and stirred with a hot plate magnetic stirrer at medium speed for 1 hour. The solid charcoal was separated from the mixture by filtration and washed twice with distilled water. The obtained solid charcoal was heated in an oven at  $110^\circ\text{C}$  for 2 hours and was followed by heating at  $300^\circ\text{C}$  for 2 hours to produce AC.

In the second step, the sulfonation process was carried out by mixing 90 mesh AC powder into various concentrated sulfuric acid solutions with a ratio of 1:5 (w/v). The sulfuric acid was prepared in various concentrations of 60%, 80%, and 98%, respectively. The mixture was heated at  $120^\circ\text{C}$  and stirred with a hot plate magnetic stirrer for 2 hours. The solids were separated from the mixture by vacuum filtration and washed with distilled water until the pH of the filtrate was neutral. Then, the filtrate was heated in an oven at  $70^\circ\text{C}$  for 12 hours to produce SAC. Three types of obtained catalysts were then signed as SAC 60, SAC 80, and SAC 98.

#### 3) Characterization of sulfonated activated carbon (SAC)

The characterization of AC, SAC 60, SAC 80, and SAC 98 catalysts was carried out to analyze the crystal phase, morphology, and acidity properties. The crystalline phase was analyzed by using a Philips D2 Phaser x-ray diffractometer at a diffraction angle range of  $10 - 80^\circ$  of  $2\theta$ . The morphology of the catalyst surfaces was imaged by using scanning electron microscopy (Hitachi Flex-SEM 100). The acidity of the catalysts was determined gravimetrically by using ammonia adsorption, while the acid sites and  $-\text{SO}_3\text{H}$  group were analyzed by a Fourier transform infrared (FTIR) spectroscopy (Shimadzu IR-Prestige 21).

#### 4) Preliminary catalytic test in the hydrolysis of cellulose

Empty palm bunches of waste (EPBW) were collected from a CPO factory in Bengkulu Indonesia. The pre-treatment process of EPBW includes washing, drying, cutting, and grinding. The obtained powder was then sieved by 90 mesh to produce the powder of raw material of cellulose. For the delignification process, the powder of cellulose raw material was immersed in a 10% KOH solution for 24 hours. The mixture was heated in an autoclave at 110 °C for 4 hours. Then, the mixture was filtered by using a vacuum filter and washed with distilled water repeatedly until the pH of the filtrate was neutral. The obtained solid material is raw cellulose for catalytic tests.

To ease the hydrolysis process, the destruction of crude cellulose was carried out by immersion in an ionic liquid of 1-butyl-3-methylimidazolium chloride (BMIMCl) with a ratio of 1:10 (w/w) [7]. The mixture was heated at 110 °C and stirred at medium speed on the hot plate stirrer for 60 minutes. After the mixture was cooled at room temperature, a total of 5 ml of distilled water was added to the mixture and was then centrifuged at 2500 rpm for 10 minutes. The supernatant was separated from the pellet and removed. The pellet was added 40 ml of distilled water and was centrifuged again at 2500 rpm for 15 minutes. The pellet was separated from the supernatant and used for further experiments on the hydrolysis test of cellulose.

The catalyst tests for the hydrolysis of cellulose were carried out by using a stainless vessel batch reactor in an autoclave [10]. The pre-treated cellulose, SAC catalysts, and distilled water were mixed with a ratio of 10:1:4 (w/w/v) and placed in the reactor. Then, the reactor was placed in the autoclave and heated at a temperature of 130 – 140 °C for 4 hours. The mixture was cooled and filtered to obtain the liquid product. The obtained liquid product was tested qualitatively by using Fehling's reagent to identify the presence of reducing sugars.

### 3. Results and Discussion

#### 3.1. X-ray diffractograms (XRD) analysis

The diffractogram patterns of the AC, SAC 60, SAC 80, and SAC 98 catalysts were shown in Figure 1. Overall, the diffractogram catalysts have similar patterns with two broad peaks in the range of 20°–30° and 40°–50°. These peaks indicate the AC, SAC 60, SAC 80 and SAC 98 catalysts were amorphous materials. The presence of a broad peak at 20°–30° was associated with C (002) of the amorphous carbon structure containing randomly oriented aromatic carbon sheets. Whereas, peaks with lower intensity and broad at 40°–50° corresponded to C (101) in the graphite structure. These facts describe the crystallinity of carbon catalysts cannot be changed by the sulfonation process. However, the sulfonation process weakens the carbon sheet as the bonds break and increases the structural irregularity of the carbon [6].

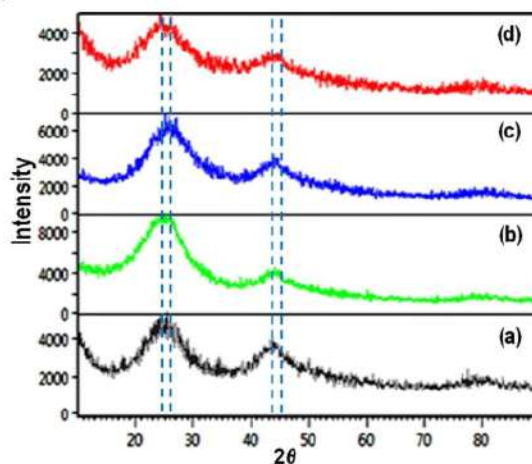


Fig. 1. The XRD patterns of (a) AC, (b) SAC 60, (c) SAC 80, and (d) SAC 98.

### 3.2. SEM Images analysis

The SEM images of non-sulfonated activated carbon and the sulfonated activated carbon catalysts were shown in Fig. 2. As shown in Fig. 2a, the morphology of AC surface was clearer and smoother compared to SAC 60 (Fig. 2b), SAC 80 (Fig. 2c) and SAC 98 (Fig. 2d). Increment of acid concentration during the sulfonation process was increased the damage percentage of the catalyst surface. In addition, the sulfonation process leads to the porous structure being rough and covered by  $-\text{SO}_3\text{H}$  groups.

SEM image of AC shows clear, demonstrating in detail the surface morphology of these materials. The micrographs appearing in Fig. 2a and c exhibit an irregular and heterogeneous surface morphology with a well-developed and accented porous structure, characteristic of carbonized organic waste [14]. The SEM micrographs of the sulfonated carbon catalyst surface morphology, shown in Fig. 4b and d, indicate a porosity decrease. This fact can be attributed to small defects, partial oxidation, condensation, and partial destruction of the porous structure arising from the strong sulfonating agent after the carbon functionalization process [13],[15]. It can also be inferred from the micrograph analysis that the partial pore blockage occurs due to the adsorption of  $-\text{SO}_3\text{H}$  groups on the carbon support catalyst, confirming the efficiency of the sulfonation process [8].

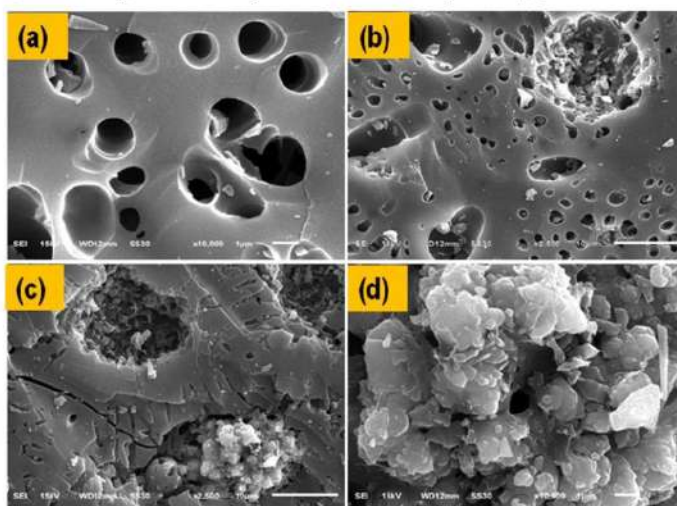


Fig. 2. The SEM image of (a) AC, (b) SAC 60 (c) SAC 80, and (d) SAC 98

### 3.3. FTIR spectrum analysis

The absence and existence of a sulfonate ( $-\text{SO}_3\text{H}$ ) group attached to the activated carbon were identified by FTIR as shown in Fig. 3. The spectrum of AC was not shown the presence of the  $-\text{SO}_3\text{H}$  group because there were no peaks at  $3400\text{ cm}^{-1}$  and  $1111\text{ cm}^{-1}$  (see Fig. 3a). Whereas, the spectra of SAC 60 (Fig. 3b), SAC 80 (Fig. 3b) and SAC 98 (Fig. 3c) show the presence of peaks in the range of  $3448.52 - 3425.58\text{ cm}^{-1}$  and  $1179.67 - 1111\text{ cm}^{-1}$ . These peaks represent the characteristic absorption of  $-\text{SO}_3\text{H}$  groups on the SAC catalyst. Table 1 shows the acidity of SAC catalysts were higher than that of AC catalyst. The acidity of the catalyst tends to increase with the increase in the concentration of sulfuric acid as a sulfonation precursor, which means that more sulfonate groups are bound to the activated carbon surface. It is well known the impregnated sulfonate group increases the acidity of the activated carbon catalysts. The high acidity of SAC catalysts can accelerate the hydrolysis of cellulose into glucose or simple sugar.

Table 1. The acidity of non- and sulfonated activated carbon catalysts

Catalysts	Acidity (mmol $\text{NH}_3/\text{g}$ catalyst)
AC	0.0064
SAC 60	0.0146
SAC 80	0.0217
SAC 98	0.0255

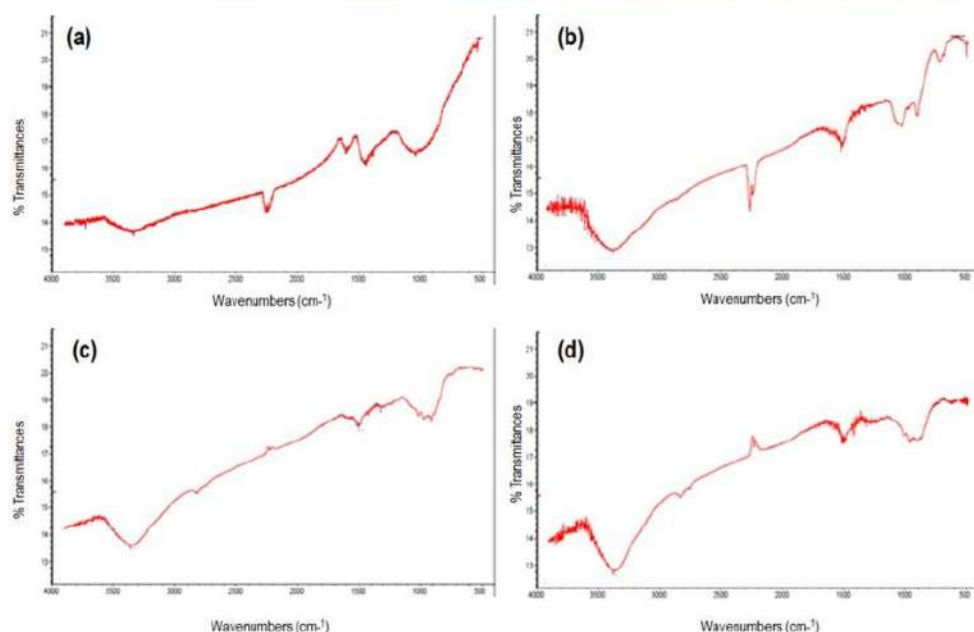


Fig. 3. Figure 3. FTIR spectra of catalysts: (a) AC, (b) SAC 60, (c) SAC 80, and (d) SAC 98.

#### 3.4. Catalytic test

As described above, the hydrolysis process of the palm bunches cellulose bunches had been previously delignated with 10 % KOH solution and then followed by destruction with ionic liquid of BMIMCl. The SEM images of palm bunches of cellulose before and after pre-treatment with ionic liquid of BMIMCl were shown in Fig.4. The BMIMCl interacted with the lamellar structure of cellulose and the weak internal chemical bond of cellulose. Due to the palm bunch, cellulose fiber is not completely soluble in BMIMCl, consequently, the cellulose depolymerization and hydrolysis reactions are inhibited and only a small part of the cellulose is broken down.

In preliminary experimental limits, the SAC catalysts can help hydrolyze palm fruit bunch cellulose into reduced sugars. As seen in Fig. 5, Fehling's reagent tests show positive results on the liquid product of hydrolysis of palm bunch cellulose. A brownish-red precipitate at the bottom of the test tube indicated qualitatively the presence of simple reduced sugars (simple sugar). However, it is well known that Fehling's reagent tests are less precise enough to identify the type of simple sugar. Therefore, further analysis is needed to ensure the type of reduced sugar in cellulose hydrolysis products.

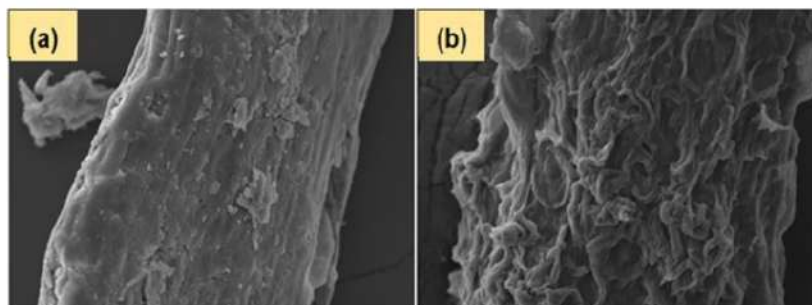
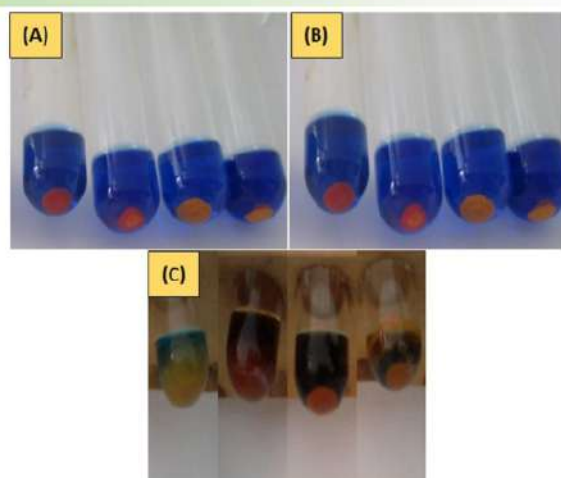


Fig. 4. The SEM images of palm bunch cellulose (a) before and (b) after treatment in BMIMCl.



**Fig. 5.** Fehling tests of the liquid product of hydrolysis of palm bunch cellulose by using activated carbon-based catalysts: (a) SAC 60, (b) SAC 80, and (c) SAC 98

#### 4. Conclusion

The activated carbon-based catalysts such as AC, SAC 60, SAC 80, and SAC 98 have been successfully synthesized from palm kernel shells in this work. Based on the XRD analysis, the crystallinity of AC and SAC catalysts were amorphous form. The presence of  $-SO_3H$  groups on the surface of activated carbon-based catalyst has no positive effect on the crystallinity form. The SEM characterization shows the morphology of the AC surface was quite clear and smooth than the SAC catalyst. This means the sulfonation process affects the structure and pores on the surface. The green SAC catalysts may be a potential catalyst for the hydrolysis of palm bunch cellulose to simple sugar.

#### Acknowledgment

We acknowledge to Professorship Acceleration Program Universitas Ahmad Dahlan 2022 for financial support.

#### References

- [1] A. Onda, "Selective hydrolysis of cellulose and polysaccharides into sugars by catalytic hydrothermal method using sulfonated activated carbon," *Journal of the Japan Petroleum Institute*, Vol. 55, No. 2, pp. 73-86, September 2012, <https://doi.org/10.1627/jpi.55.73>.
- [2] K. Ngaosuwana, J. G Goodwin, and P. Prasertdham, "A green sulfonated carbon-based catalyst derived from coffee residue for esterification," *Renewable Energy*, Vol 86, pp. 262 – 269, February, 2016, <https://doi.org/10.1016/j.renene.2015.08.010>
- [3] W. Mateo, H. Lei, E. Villota et al, "Synthesis and characterization of sulfonated activated carbon as a catalyst for bio-jet fuel production from biomass and waste plastics," *Bioresource Technology*, Vol 297, February 2020, <https://doi.org/10.1016/j.biortech.2019.122411>.
- [4] S. Niu, Y. Ning, C. Lu et al, "Esterification of oleic acid to produce biodiesel catalyzed by sulfonated activated carbon from bamboo," *Energy Conversion and Management*, Vol 163, pp. 59 – 65, May 2018, <https://doi.org/10.1016/j.enconman.2018.02.055>.
- [5] T. Zhang, W. Li, Y. Jin, and W. Ou, "Synthesis of sulfonated chitosan-derived carbon-based catalysts and their applications in the production of 5-hydroxymethylfurfural," *International Journal of Biological Macromolecules*, Vol 157, pp. 368–376, August, 2020, <https://doi.org/10.1016/j.IJBIOMAC.2020.04.148>.
- [6] F. Fahmi, W. Widiyastuti, and H. Setyawan, "Graphitization of coconut shell charcoal for sulfonated mesoporous carbon catalyst preparation and its catalytic behavior in the esterification reaction," *Bulletin*

- of Chemical Reaction Engineering & Catalysis, Vol 15, No.2, pp 538–544, July 2020, <https://doi.org/10.9767/bcrec.15.2.7745.538-544>.
- [7] J. Kaszyńska, A. Rachocki, M. Bielejewski, and J. Tritt-Goc, "Influence of cellulose gel matrix on BMIMCl ionic liquid dynamics and conductivity," *Cellulose*, Vol 24, No.4, pp. 1641 – 1655, February 2017, <https://doi.org/10.1007/s10570-017-1223-z>.
- [8] P. Engel, L. Hein, and A. C. Spiess, "Derivatization-free gel permeation chromatography elucidates enzymatic cellulose hydrolysis," *Biotechnology for Biofuels*, Vol 5, No. 77, October 2012, <http://www.biotechnologyforbiofuels.com/content/5/1/77>.
- [9] Y. Ning, and S. Niu, "Preparation and catalytic performance in the esterification of a bamboo-based heterogeneous acid catalyst with microwave assistance," *Energy Conversion and Management*, Vol 153, pp. 446 – 454, December 2017, <https://doi.org/10.1016/j.enconman.2017.10.025>.
- [10] D. S. Tong, X. Xia, X. P. Luo, et al "Catalytic hydrolysis of cellulose to reduce sugar over acid- activated montmorillonite catalysts," *Applied Clay Science*, Vol 74, pp. 147–153, April 2013, <https://doi.org/10.1016/J.CLAY.2012.09.002>
- [11] A. P. da Luz Corrêa, R. R. C. Bastos, G. N. da Rocha Filho, J. R. Zamian et al. "Preparation of sulfonated carbon-based catalysts from murumuru kernel shell and their performance in the esterification reaction," *RSC Advances*, Vol. 10, No. 34, pp. 20245–20256, May 2020, <https://doi.org/10.1039/d0ra03217d>.
- [12] A. P. Bora, S. H. Dhawane, K. Anupam, and G. Halder, "Biodiesel synthesis from Mesua ferrea oil using waste shell derived carbon catalyst," *Renewable Energy*, Vol 121, pp. 195 – 204, June 2018, <https://doi.org/10.1016/j.renene.2018.01.036>.
- [13] Y. Zhou, S. Niu, and J. Li, "The activity of the carbon-based heterogeneous acid catalyst derived from bamboo in the esterification of oleic acid with ethanol," *Energy Conversion and Management*, Vol 114, pp. 188–196, April 2016, <https://doi.org/10.1016/J.ENCONMAN.2016.02.027>.
- [14] S. H. Dhawane, T. Kumar, and G. Halder, "Recent advancement and prospective of heterogeneous carbonaceous catalysts in the chemical and enzymatic transformation of biodiesel," *Energy Conversion and Management*, Vol 167, pp 176–202, July 2018, <https://doi.org/10.1016/J.ENCONMAN.2018.04.073>.
- [15] N. Liu, A. B. Charrua, C. H. Weng, X. Yuan, and F. Ding "Characterization of biochars derived from agriculture wastes and their adsorptive removal of atrazine from aqueous solution: A comparative study," *Bioresource Technology*, Vol 198, pp. 55 – 62, December 2015, <https://doi.org/10.1016/j.biortech.2015.08.129>.



# HASIL CEK\_Artikel Chemica

---

## ORIGINALITY REPORT

---

11%

SIMILARITY INDEX

7%

INTERNET SOURCES

13%

PUBLICATIONS

2%

STUDENT PAPERS

---

## PRIMARY SOURCES

---

1

[patents.glgoo.top](https://patents.google.com/)

Internet Source

1%

---

2

Jhessica M. Fonseca, Lucas Spessato, André L. Cazetta, Camila da Silva, Vitor de C. Almeida.

"Sulfonated carbon: synthesis, properties and production of biodiesel", Chemical

Engineering and Processing - Process

Intensification, 2022

Publication

1%

---

3

Daouda Kouotou, Mohammed Ghalit, Julius Nsami Ndi, Luisa M. Pastrana Martinez et al.

"Removal of metallic trace elements (Pb<sup>2+</sup>, Cd<sup>2+</sup>, Cu<sup>2+</sup>, and Ni<sup>2+</sup>) from aqueous solution by adsorption onto cerium oxide modified

activated carbon", Environmental Monitoring and Assessment, 2021

Publication

1%

---

4

Johnson Olumuyiwa Agunsoye, Joachin Eberechukwu Anyanwu, Sefiu Adekunle Bello, Suleiman Bolaji Hassan. "Effect of Particle

Sizes on some Mechanical Properties of

1%

# Kernel Shell Reinforced Al-Mg-Mn Composites", Nano Hybrids and Composites, 2022

Publication

---

- 5 Juliana L. Vidal, Olivia M. Wyper, Stephanie L. MacQuarrie, Francesca Maria Kerton. "Ring - Closing C - O/C - O Metathesis of Aliphatic Ethers and Esterification of Terpene Alcohols Catalyzed by Functionalized Biochar", European Journal of Organic Chemistry, 2021 1 %
- Publication
- 

- 6 Morina Adfa, Fio Livandri, Neva Putri Meita, Syalfinaf Manaf et al. "Termiticidal activity of Acorus calamus Linn. rhizomes and its main constituents against Coptotermes curvignathus Holmgren", Journal of Asia-Pacific Entomology, 2015 1 %
- Publication
- 

- 7 [mdpi-res.com](https://www.mdpi-res.com) 1 %
- Internet Source
- 

- 8 Huayu Wang, Changbin Zhang, Hong He, Lian Wang. "Glucose production from hydrolysis of cellulose over a novel silica catalyst under hydrothermal conditions", Journal of Environmental Sciences, 2012 1 %
- Publication
- 

- 9 Thi Tuong Vi Tran, Suwadee Kongparakul, Prasert Reubroycharoen, Guoqing Guan, 1 %

Manh Huan Nguyen, Narong Chanlek, Chanatip Samart. "Production of furan based biofuel with an environmental benign carbon catalyst", Environmental Progress & Sustainable Energy, 2017

Publication

---

10

Totok Eka Suharto, Irfan Gustian, Elvita Nur Hasanah, Is Fatimah. "COMPOSITE OF POLYSTYRENE/ACTIVATED CARBON FROM COAL TAILING/PLATINUM AS AN ELECTRODE CANDIDATE FOR MEMBRANE FUEL CELL", RASAYAN Journal of Chemistry, 2022

Publication

---

11

Bahrani Anggi Sinta. "Hubungan budaya organisasi dengan loyalitas kerja pegawai di sekolah", Journal of Islamic Education and Innovation, 2022

Publication

---

12

Robert-Jan van Putten, Jan C. van der Waal, Ed de Jong, Carolus B. Rasrendra, Hero J. Heeres, Johannes G. de Vries. "Hydroxymethylfurfural, A Versatile Platform Chemical Made from Renewable Resources", Chemical Reviews, 2013

Publication

---

13

[www.journal.uad.ac.id](http://www.journal.uad.ac.id)

Internet Source

---

1 %

1 %

1 %

1 %

14 Submitted to Institute of Graduate Studies,  
UiTM 1 %  
Student Paper

---

15 Submitted to University of Huddersfield 1 %  
Student Paper

---

16 jurnal.ugm.ac.id 1 %  
Internet Source

---

17 Submitted to University of Strathclyde 1 %  
Student Paper

---

Exclude quotes On

Exclude matches < 1%

Exclude bibliography On